

TEST REPORT

Order no: 81A31327

Signature: SL/Z-134/EN45545-R21/0129a/2025

Police, 19.02.2025

Tests methods:

1. EN ISO 5659-2:2017. Plastic – Smoke generation – Part 2: Determination of optical density by a single – chamber test.
2. ISO 5660-1:2015/Amd.1:2019. Reaction to fire tests – Heat release, smoke production and mass loss rate – Part 1: Heat release rate (cone calorimeter method).
3. EN 17084:2018. Railway applications – Fire protection of railway vehicles – Toxicity test of materials and components.
4. EN 45545-2:2020+A1:2023. Railway applications – Fire protection on railway vehicles – Part 2: Requirements for fire behavior of materials and components

Content of request: Tests according to EN 45545-2:2020+A1:2023 - requirement R21.

Sponsor: Camira Transport Fabrics Ltd
Hopton Mills
Mirfield HD9 4 AY, United Kingdom

Material: Aura + Acrylic Backcoat + NitroPhlam365

Composition/specification: **Composition details:**
Pile: 70% Wool, 18% Polyester, 12% Nylon
Ground: 100% Cotton
Batch Number: 557592 (200)
Pattern reference: CAA326
Fabric Type: Upholstery Fabric

Manufacturer/supplier: Camira Transport Fabrics Ltd
Hopton Mills
Mirfield HD9 4 AY, United Kingdom

Assessment: The tested product fulfils the requirement of R21 according to EN 45545-2:2020+A1:2023 for hazard level HL1, HL2 and HL3.

The reprint and the copying: only with the agreement of Camira Transport Fabrics Ltd

Without the written consent of the Sychta Laboratory the report can be copied only in one piece.

Report applies only to the sample tested and is not necessarily indicative of the qualities of apparently identical or similar products.

Content of test report: six pages with signature and numbers.

1. Smoke generation according to EN-ISO 5659-2 + EN 45545-2

Tested side: coated side.

Test conditions - irradiance of $25 \text{ kW} \cdot \text{m}^{-2}$ with pilot flame.

Table 1.1. Final findings of smoke generation

Name of measured quantity	Unit	Specimen			Average	Standard deviation
		1	2	3		
Mass of specimen	g	16,2	17,5	16,7	16,8	0,7
Specimen thickness	mm	23,2	23,2	23,2	23,2	0
Ignition time - t_z	s	12	5	1	6	6
Extinction time	s	-	-	-	-	-
Duration of the test	s	600	600	600	600	0
Maximum of specific optical density - $D_{s,max}$	-	64	48	44	52	10
Time of arrival of the maximum of $D_{s,max}$	s	600	600	600	600	0
Specific optical density in the first 4 min of the test - $D_s(4)$	-	54	31	26	37	15
Cumulative specific optical densities in the first 4 min of the test - VOF_4	min	79	31	53	54	24

Remarks: none.

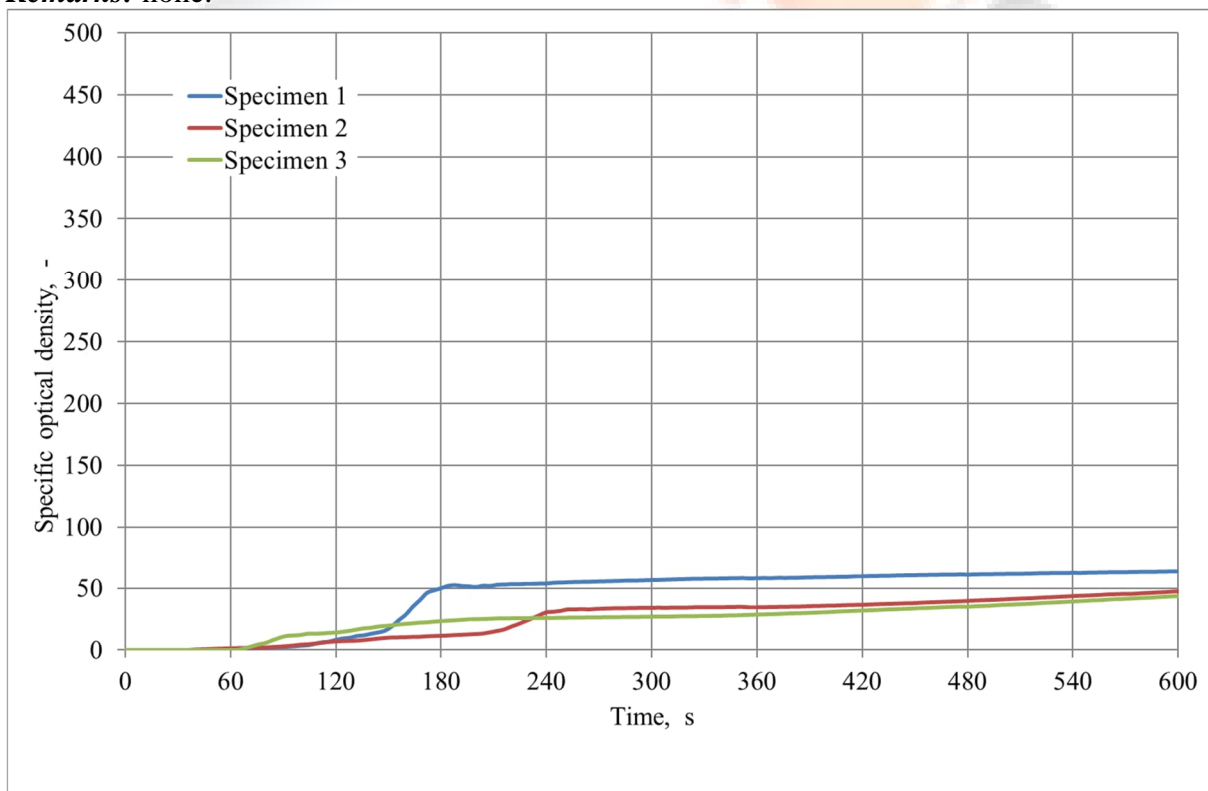


Figure 1.1. Specific optical density in the time

2. Results of toxic products emission of material decomposition and burning according to EN 17084, Method 1

Test conditions - irradiance of $25 \text{ kW} \cdot \text{m}^{-2}$ with pilot flame.

Table 2.1. Concentration of toxic products of material decomposition and burning after 4 min

Toxic component of burning products	Concentration of toxic products after 4 min				
	Specimen no.			Average	Standard deviation
	1	2	3		
	mg·m ⁻³				
CO ₂	48940	35340	51350	45210	8630
CO	18	20	23	20	3
HCN	10	13	8	10	3
NO ₂	3	0	0	0	2
NO	24	30	31	26	4
HCL	0	0	0	0	0
SO ₂	128	104	137	123	17
HF	0	0	0	0	0
HBr	0	0	0	0	0

Table 2.2. Concentration of toxic products of material decomposition and burning after 8 min

Toxic component of burning products	Concentration of toxic products after 8 min				
	Specimen no.			Average	Standard deviation
	1	2	3		
	mg·m ⁻³				
CO ₂	6905	6869	7471	7082	337
CO	72	69	80	74	6
HCN	16	16	11	114	23
NO ₂	7	0	0	2	4
NO	47	51	48	49	2
HCL	0	0	0	0	00
SO ₂	165	147	165	159	11
HF	0	0	0	0	0
HBr	0	0	0	0	0

Table 2.3. Conventional index of toxicity

Name of measured quantity	Unit	Specimen			Average	Standard deviation
		1	2	3		
Conventional index of toxicity CIT _G at 4 min	-	0,12	0,12	0,13	0,12	0,00
Conventional index of toxicity CIT _G at 8 min	-	0,20	0,19	0,18	0,19	0,01

Remarks: none.

3. Heat release rate of specimen according to ISO 5660-1

Test conditions - irradiance of $25 \text{ kW} \cdot \text{m}^{-2}$

Table 3.1. Heat release rate

Name of measured quantity	Unit	Specimen			Average	Standard deviation
		1	2	3		
Mass of the specimen	g	50,9	52,3	51,5	51,6	0,7
Specimen thickness	mm	49,3	49,5	49,3	49,4	0,1
Ignition time	s	98	96	110	101	8
Extinction time	s	1002	952	1034	996	41
Duration of the test	s	1200	1200	1200	1200	0
Maximum heat release rate	$\text{kW} \cdot \text{m}^{-2}$	102,5	127,7	107,2	112,5	13,4
Total heat release	$\text{MJ} \cdot \text{m}^{-2}$	37,3	30,2	37,0	34,8	4,0
Maximum average rate of heat emission MARHE	$\text{kW} \cdot \text{m}^{-2}$	46,6	36,3	41,7	41,5	5,1
Fire integrity acc. 5.2.2.2 EN 45545-2	YES/NO	YES	YES	YES	YES	-

Remarks: none.

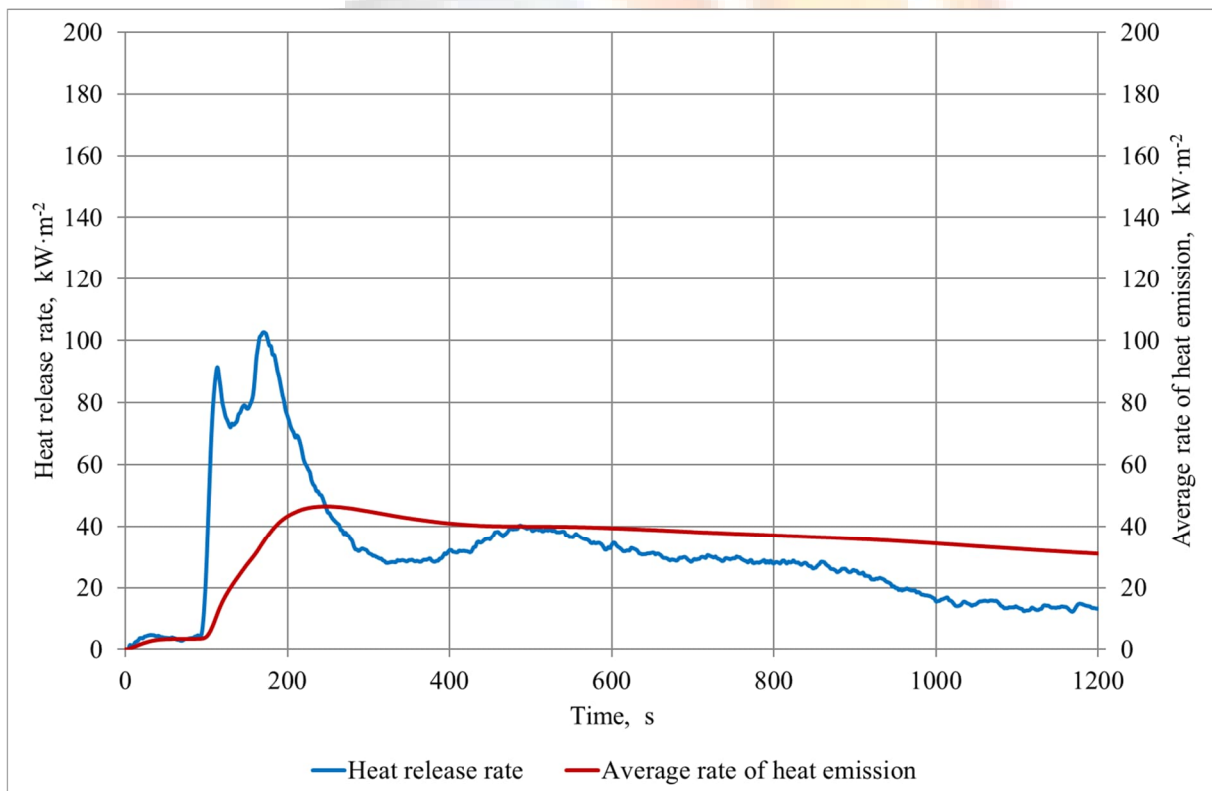


Figure 3.1. The relation of heat release rate and the time – specimen 1

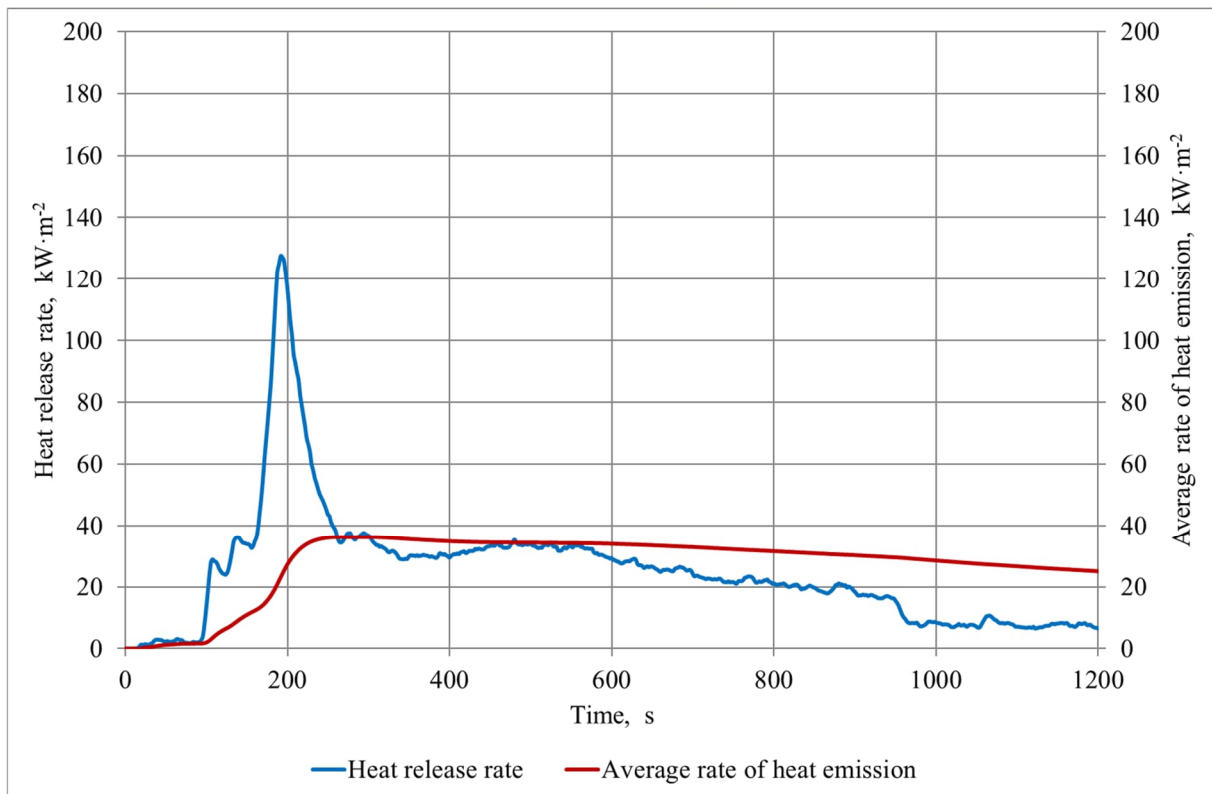


Figure 3.2. The relation of heat release rate and the time – specimen 2

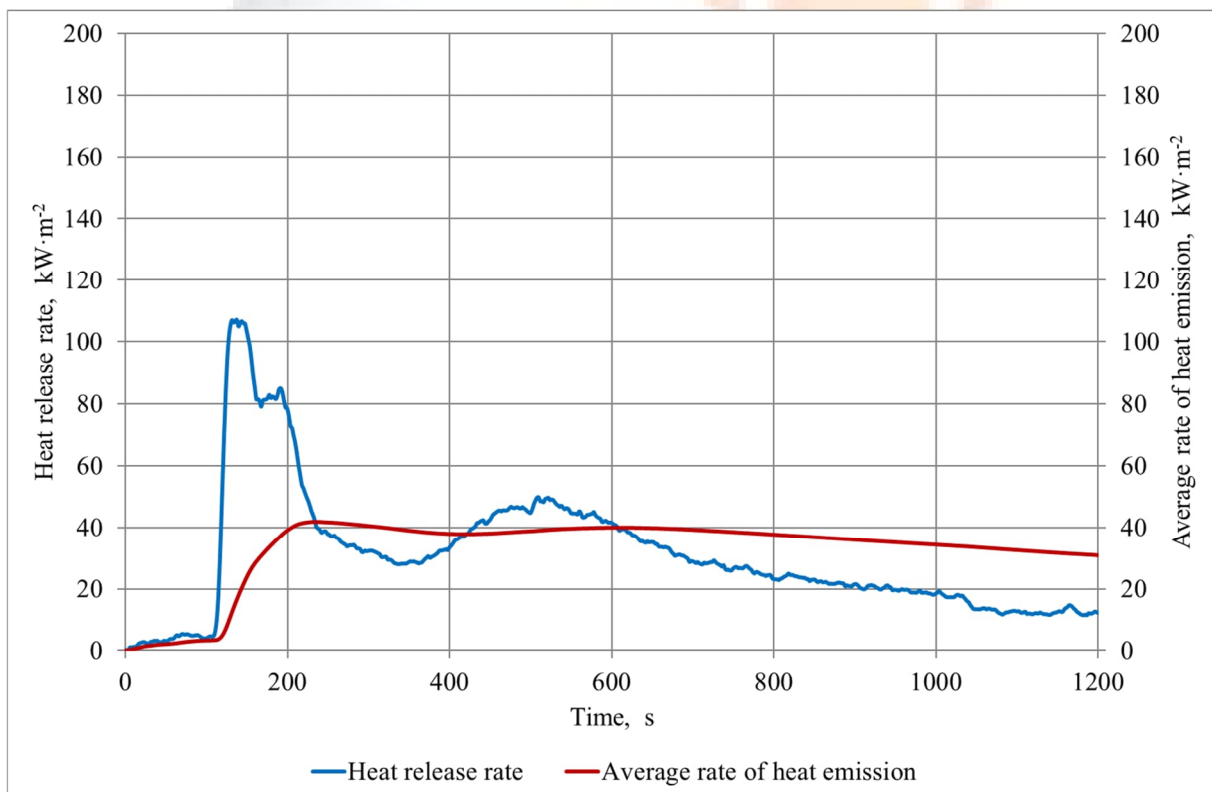


Figure 3.3. The relation of heat release rate and the time – specimen 3

4. Final findings

Requirement	Method/norm	Measured quantity	Unit	Measured value	Critical value			Crossing coefficient		
					HL1	HL2	HL3	HL1	HL2	HL3
R21	T03.02 EN ISO 5660-1: 25 kW·m ⁻²	MARHE	kW·m ⁻²	41,5	75	50	50	0,55	0,83	0,83
	T10.03 EN ISO 5659-2: 25 kW·m ⁻²	D _s max	-	52	300	300	200	0,17	0,17	0,26
	T11.02 EN 17084 Method 1 25 kW·m ⁻²	CIT _G (4)	-	0,12	1,2	0,9	0,75	0,10	0,14	0,16
		CIT _G (8)	-	0,19	1,2	0,9	0,75	0,16	0,21	0,25

The tested product fulfils the requirement of R21 according to EN 45545-2:2020+A1:2023 for hazard level HL1, HL2 and HL3.

5. Remaining required information

Date of receipt of samples: 10.02.2025

Sampling: Sponsor took and delivered samples.

Description of the test material: upholstery set consisting of: patterned, in blue upholstery described "Aura" fabric 4 mm thick with a weight per unit area of 980 g/m² + white fireproof fabric ~0,2 mm thick with a weight per unit area of approx. 250 g/m² + and graphite foam with density approx. 92 kg/m³. Sponsor delivered one piece of upholstery fabric with dimensions 715-730x640 mm, one piece of fireproof fabric with dimensions 690x1000 mm and one piece with dimensions 765x430 mm, 6 samples of graphite foam with dimensions 100x100x43-44 mm and 6 samples with dimensions 75x75x19-20 mm. Laboratory prepared the samples



Conditioning of specimens: constant mass at a temperature of 23±2°C, and relative humidity of 50±5 %.

Specimen preparation: according to Clause 7.5 of ISO 5660-1:2015+Amd:2019.

Declarations:

1. The test results relate to the behaviour of the test specimens under the particular conditions of the test; they are not intended to be the sole criterion for assessing the potential fire hazard of the products in use.
2. The information provided on the first page of the report concerning the scope of research and identification of the tested object/objects were provided by the Sponsor.

Operators:

dr hab. Zygmunt Sychta
mgr inż. Andrzej Sychta

SYCHTA LABORATORIUM Sp. J.
72-010 Police, ul. Ofiar Stutthofu 90
tel./fax +48 91 4210 214, tel. 502078855
e-mail: biuro@sychta.eu www:sychta.eu
KRS 0000387681 REGON 321023120
NIP 8513152392

Authorised by:

KIEROWNIK TECHNICZNY
dr inż. Krzysztof Sychta

Date and place of test - 13-14.02 and 18.02.2025, Police